

Experimental Investigation on Tensile Strength of Concrete with Verbascum Herbal Additive

Taleb Moradi Shaghaghi¹

¹ Department of civil engineering, College of Engineering, Tabriz branch, Islamic Azad University, Tabriz, Iran

Abstract: Due to the high usage of concrete in construction, civil engineers try to decrease the defects of concrete and increase the benefits of it by using some methods. One of these methods is adding additive materials in order to achieve mentioned target. Undoubtedly in the usage of these materials engineers should pay attention to economic issues, decreasing costs of project and their availability. Most of these additive materials used in concrete, are chemicals and albeit they improve some properties of concrete they have some negative effects on other features of it.

In this investigation an herbal additive material is used in concrete, this herbal material is the powder of the leaves of a plant named Mahur or Khargushak) *Verbascum Thapsus*) that grows in the mountains naturally. The experimental results of specimens in this investigation indicate that adding this herbal material during concrete mixing increases tensile strength 20% to 25%. Due to the significant increase in tensile strength of concrete by adding the powder of Mahur additive, the surficial cracks of concrete decrease. By the way the amount of used cement in order to reach to a specific strength decreases.

Keywords: *Verbascum Thapsus* (Mahur), Tensile Strength of concrete, Water per Cement ratio

1. Introduction

In construction, concrete consumption due to the immense benefits in various application and different forms, is increasing; In fact, the most widely used building material is concrete. Per capita production of structural concrete in the world is around one tone per person in the year. It means in the world about 6 milliard tons of concrete are produced and consumed each year and this production and consumption increases about 1 to 1.5 percent each year. The most important ingredient of concrete is cement. According to Consumption statistics of concrete and cement, a considerable amount of dust and air emissions and Greenhouse Gases, resulting from the production of cement and concrete consumption are produced which can be a serious threat to the human's environment. Per production of each tone of cement Klinger, about 1.3 tones CO₂ gas and about 160 Kg dust is sent to the air.

The entire world now is aware of their obligation and duty to consider environmental protection and sustainable development. Man believes that all human are affected by adverse environmental impacts arising from the development. Undesirable and harmful effects of producing Greenhouse gases in increasing global temperature, melting polar ice, changing climate and the destruction of Ozon layer are not exclusive to any particular country, but they are universal subjects. Therefore, necessary actions for minimizing the harmful effects of cement and concrete production and consumption, is a public duty and responsibility.

On the other hand, construction increasing and as its result increasing in production and consumption of concrete for the sustainable development of any country is essential. So the engineering societies and science manufacturing centers, should take serious actions with proper planning to increase advantages of concrete and reduce its adverse effects. To improve the quality of the concrete industry and its alignment with the environment and sustainable development, effective steps should be taken. In this regard, increasing mixed and

Pozzolanic cements and replacing part of cement with materials in order to reduce Klinger consumption, can be good solution to achieve the aforementioned goals.

Using Verbascum plant powder as an additive material in concrete mixing reduces cement consumption and increase and tensile strength of concrete and improves some concrete mechanical properties of the concrete.

In this paper, the concrete specimens containing Verbascum plant powder with different amount as a percentage of the cement weight is provided and tensile strength is tested and the obtained results are discussed.

2. Laboratory Samples

2.1. Sample Specifications

As it was introduced in the project objectives part, in order to determine the effects of different amounts of Verbascum plant powder in tensile strength of concrete and determine its optimum amount, seven different amount of Verbascum powder as a percentage of cement weight has been used in a concrete with fixed mixture. On the other hand, it's likely that with increasing amount of Verbascum powder, amount of concrete water reduces. (The number of concrete slump is reduced). This will increase the strength of concrete because of this the water –cement ratio is considered as one of the research's variables.

Thus the tensile strength of samples are tested and checked for a type of concrete (C25) with three different water-cement ratios (0.5 ,0.55,0.6) and for each water-cement ratio, 7 different percentage of Verbascum powder (3,2,1.5,1,0.75,0.5,0.25 percent) as an additive are used.

A sample per each water-cement ratio without Verbascum powder, as a control sample is prepared, which in the whole experiment, 42 standard cylindrical specimens to test tensile strength in the splitting tensile test, are provided. To enhance the accuracy of specimens in all samples, two specimens are prepared to check tensile strength and average strength of two samples is considered as the sample strength.

- Concrete aggregates of specimens: The aggregates used in the concrete of specimens are from Tabriz gravel and sand quarries are used and aggregate gradations are according to table 1.
- Additive powder of Verbascum plant: Verbascum plant after being dried has been crushed and powdered and with aforementioned percent as a percentage of the cement is used in the concrete specimens. Verbascum plant is a plant that grows on the mountain slopes as a weed and is abundant at Azerbaijan area of Iran.(Figure 1).In the past, crushed Verbascum plant was mixed with clay and it was used for making oven and cruse , still in some villages this method is used. From the older people points of view in villages, using this plant in the clay, increases clays strength and reduces its cracks. This effect and subject causes encouragement and motivate for this research. Flowers of Verbascum plant that have abundant mucilage, are dried in the shade and after being powdered, poured in hot water and are used for treatment of colds and chest softener .Ointments also made from the Verbascum plant powder and put on a wound for wound healing, Verbascum leaves are dried and its powder is used in fishing as bait. Verbascum plant grows mostly in Asia and Europe and it grows alit in the most temperate regions, foothills and rangelands of Iran especially in Azerbaijan. Samples of dried flowers of this plant can be found in some groceries. Verbascum has hot tempers and its flowers have lots of mucilage. This plant has sulfide compounds, calcium compounds, vitamin B and other minerals like protein and fiber. Oil of flowers of this plant in many parts of Europe is used as a home remedy for various ailments such as tuberculosis, ear infections and inflammation of the eyelids. Verbascum has properties such as expectorant, light diuretic, calming, wound repair, anti-inflammatory and is used to treat coughs and bronchitis, also Verbascum is an effective solution for hair and eyebrows growth. Verbascum was analyzed in the laboratory and its ingredients are in the table 2.According to this table, the main ingredient of this plant is nitrogen, potassium, magnesium and iron.



Fig. 1: Verbascum plant.

TABLE I: Gradation of consumption aggregate

Number of sieve	Size of the aperture of sieve	Weight remained on sieve	percentage of residue on the sieve	Cumulative percentage of residue on the	Cumulative percentage of rejected from
1	25	0	0	0	100
0.75	19	70	2.8	2.8	97.2
0.5	125	230	9.2	12	88
0.375	95	220	8.8	20.8	79.2
4	4.75	450	18	38.8	61.2
10	2	360	14.4	53.2	46.8
16	1.18	230	9.2	62.4	37.6
30	0.6	290	11.6	74	26
50	0.3	240	9.6	83.6	16.4
100	0.15	130	5.2	88.8	11.2
200	0.075	280	11.2	100	0.0

TABLE II: Ingredients of Plant

Total nitrogen	Phosphorus (P)	Potassium (K)	Magnesium (Mg)	Zinc (Zn)	Manganese (Mn)	Copper (Cu)	Iron (Fe)	Bor (B)
Percentage				mg per Kg				
1.4	0.09	0.45	0.14	22.5	64	38.5	1740	33.5

3. Laboratory

This research plan has been done at the concrete technology laboratory of the Tabriz Azad University. The equipment used are related to laboratory of the university such as ELE digital concrete breaker jack device with capacity of 200 tones and molds and other devices used in the sampling and curing of the samples.

Specimens are provided cylindrical samples in dimension 30*15 Cm for tensile strength tests in sample splitting tensile test.

4. Concrete Mixture Of Specimens

Concrete mixture of specimens for three water-cement ratio, are summarized in the table3. In this table "G" is the amounts of gravel, "S" is the amounts of sand, "C" is the amounts of cement and "W" is the amount of water per each m³ of concrete and D_c is the specific weight of fresh concrete.

5. Test Results

Standard cylindrical specimens at the age of 28 days have been tested under tensile experiment at the sample splitting tensile test. The average results of two specimens are considered as result of test sample.

Results of tensile strength of specimens in splitting tensile test, for different amounts of Verbascum powder (zero percent as control sample and 0.25 and 0.5 ,0.75,1,1.5,2percent of cement weight), and for three different water-cement ratios (0.5,0.55,0.6),are mentioned in the table 4. In this table f_{ct} tensile strength of samples concrete is calculated from this equation:

$$f_{ct} = \frac{2P}{\pi DL} = \frac{2P}{A} \quad (1)$$

In this equation "P" is compressive force of splitting time of cylindrical samples and "D" is cylinder diameter equals to 15 Cm and "L" is cylinder length equals to 30 Cm.

TABLE III: Concrete mixture in C25 concrete

Water-Cement ratio (W/C)	G (kg / m ³)	S (kg / m ³)	C (kg / m ³)	W (kg / m ³)	Dc (kg / m ³)
0.5	1115	715	350	175	2355
0.55	1115	690	350	193	2355
0.6	1115	680	350	210	2355

TABLE IV: Results of samples tensile strength tests of specimens

Row	Additive plant percentage	Water-cement ratio (W/C)	P force(Kn)	A(mm ²)	f _{ct} (Mpa)
1	0%	0.5	172.5	141300	2.44
		0.55	166.74	141300	2.36
		0.6	151.19	141300	2.14
2	0.25%	0.5	199.23	141300	2.82
		0.55	193.58	141300	2.74
		0.6	185.1	141300	2.62
3	0.50%	0.5	205.8	141300	2.91
		0.55	199.94	141300	2.83
		0.6	179.5	141300	2.54
4	0.75%	0.5	207.7	141300	2.94
		0.55	206.3	141300	2.92
		0.6	182.3	141300	2.58
5	1%	0.5	213.6	141300	3.02
		0.55	210.54	141300	2.98
		0.6	176.62	141300	2.5
6	1.5%	0.5	205.35	141300	2.91
		0.55	214.77	141300	3.04
		0.6	192.87	141300	2.73
7	2%	0.5	203.47	141300	2.88
		0.55	204.88	141300	2.9
		0.6	173.1	141300	2.45

5.1. Effects of Verbascum Powder on Tensile Strength of Concrete

Results of tensile experiments of standard cylinder samples at the age of 28 days, with different amounts of Verbascum powder and different water-cement ratios, according to table5, are shown as diagrams of figure 2. These diagrams illustrate that adding Verbascum powder to concrete, increases tensile strength of concrete. In all amounts of added Verbascum powder and water –cement ratio, increasing in strength is obvious. Amount of increasing in tensile strength depends on the amount of Verbascum powder.

Diagrams of the figure 3, illustrate changes in tensile strength of cylinder samples for water-cement ratios 0.5, 0.55, 0.6 with different amount of Verbascum powder in comparison with strength of control sample.

Verbascum powder as the percentage of cement weight is added to the concrete samples, due to the low specific weight of Verbascum powder, which is around 300 Kg per m³, low percentage of this powder, has a considerable volume.

The following results are obtained from table 5 and diagrams of figure 2 and 3.

- A. Adding Verbascum powder to concrete in all cases of experiment increases concrete tensile strength.
- B. The maximum increasing of tensile strength of concrete was when the amount of Verbascum powder used in concrete was 1.5 percent of cement weight, in this amount of Verbascum powder, concrete strength increases 19.26 percent in water-cement ratio of 0.5, and around 28.8 percent in water-cement ratio of 0.55, and 27.6 percent compared to control sample in the water-cement ratio of C .There is more increase in tensile strength of concrete by adding Verbascum powder in lower water-cement ratio

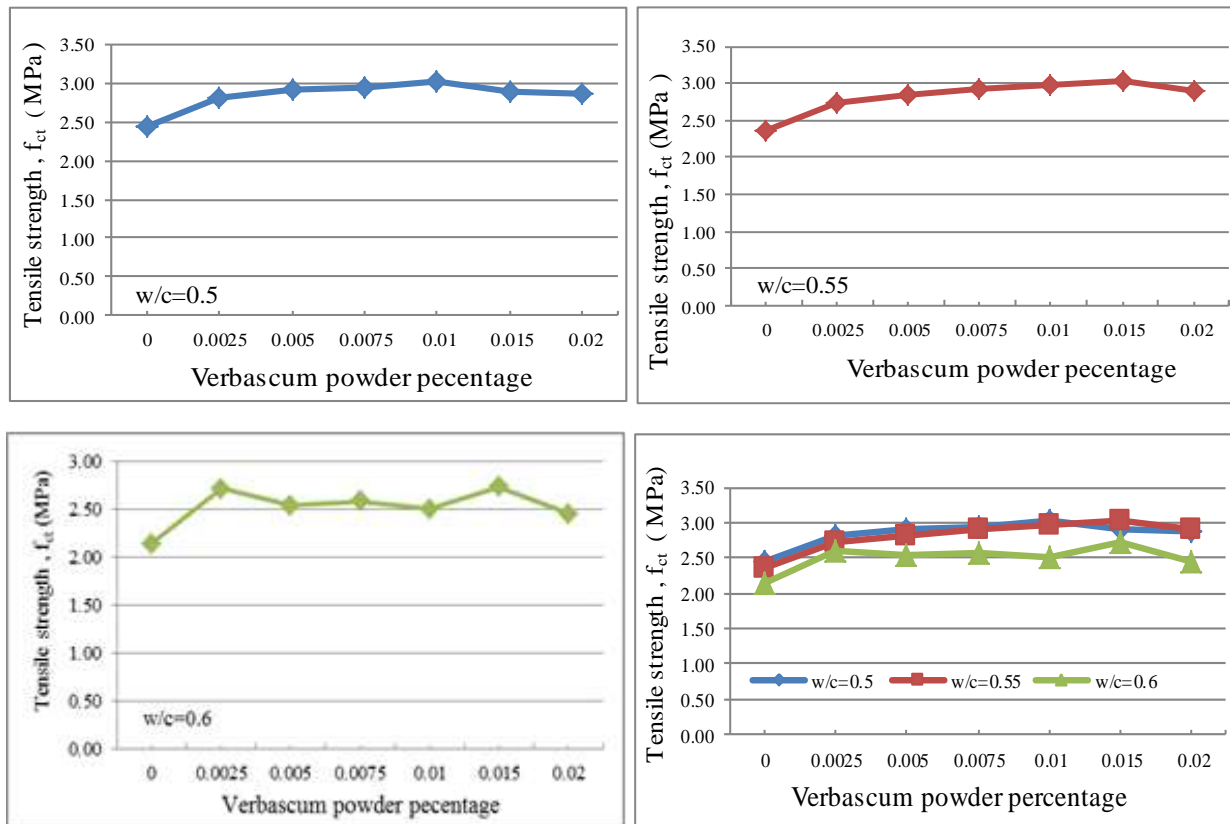
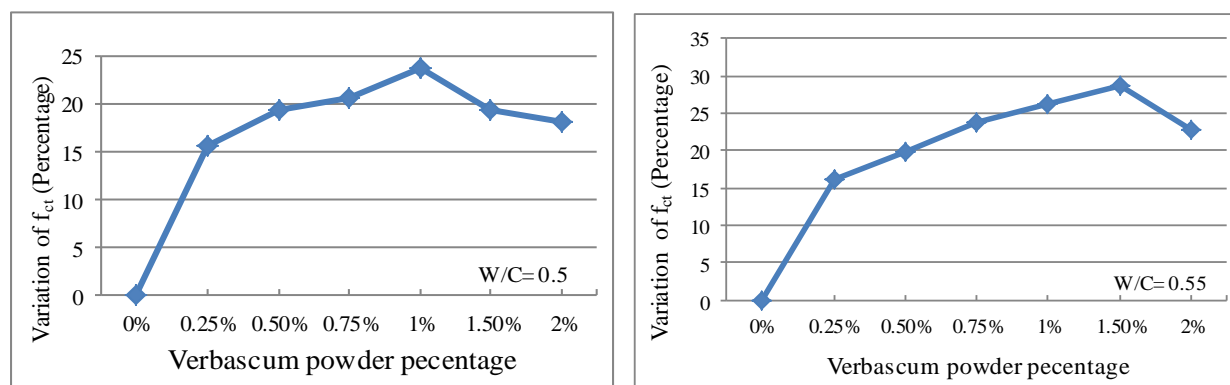


Fig. 2: Tensile strength of concrete samples containing Verbascum powder.



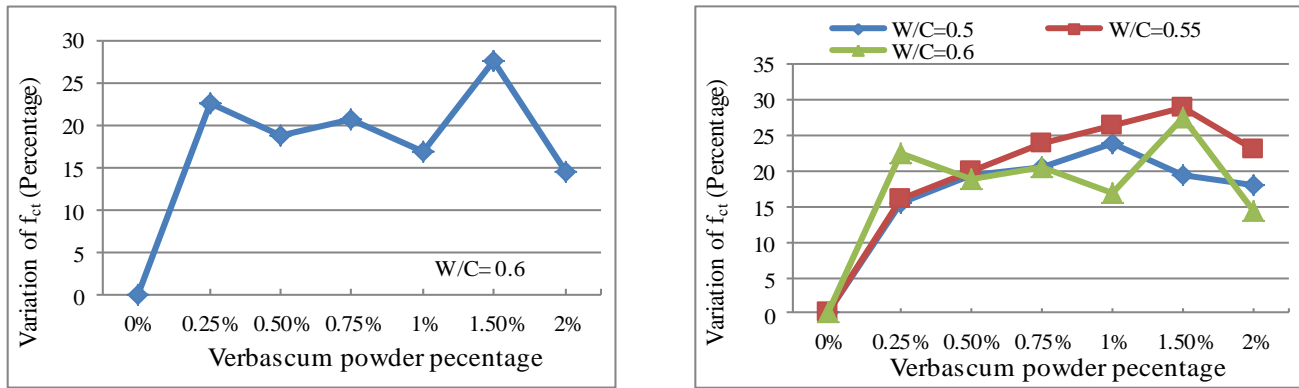


Fig. 3: Changes of tensile strength of concrete containing Verbascum powder.

6. Conclusion

According to the results of taken tests, which are provided in tables and diagrams, following results are obtained:

1. Adding Verbascum powder to concrete in all tested cases increases tensile strength of concrete around 25 percent.
2. The greatest increase in the concrete tensile strength is observed when the amount of Verbascum powder used in concrete was about 1.5 percent by cement weight.
3. There is more increasing in tensile strength of concrete by adding plant powder in lower water-cement ratio.
4. Due to the increase in tensile strength of concrete with adding Verbascum powder, this concrete will have fewer cracks as the result of shrinkage and temperature changing.

7. Acknowledgements

The author would like to thank Tabriz Branch, Islamic Azad University for the financial support of this research, which is based on a research project contract.

8. References

- [1] A.A. Ramezaniapour and A. Esmailpour, *The role of admixtures in the development of concrete technology*, 1991, Amirkabir University Edition.
- [2] A.A. Ramezaniapour, "Durability of concrete structures", *Sharif Magazine*, 1995, No.10.
- [3] A.A. Ramezaniapour, *Concrete mix design*, 1998, Science and Industry Publications.
- [4] A.A. Ramezaniapour, *Cement replacement materials*, 2014, Springer Geochemistry/Mineralogy publications.
- [5] *Prediction of creep, shrinkage and temperature effects in concrete structures, Part 1: Materials and general properties of concrete*, ACI Committee 209.R-80, ACI manual of concrete practice.
- [6] A.M. Neville and J.J. Brooks, *Concrete technology*, 2010, Prentice Hall, Pearson publication.
- [7] T.M. Shaghaghi and M.M Shaghaghi, *Design of concrete structures*, 2010, Islamic Azad University of Tabriz branch publications.